

Minimal electronic models for superconducting BiS₂ layers

Hidetomo Usui, Katsuhiko Suzuki, and Kazuhiko Kuroki

¹*Department of Engineering Science, The University of Electro-Communications, Chofu, Tokyo 182-8585, Japan*
(Dated: July 18, 2012)

We construct minimal electronic models for a newly discovered superconductor LaO_{1-x}F_xBiS₂ ($T_c = 10.6\text{K}$) possessing BiS₂ layers based on first principles band calculation. First, we obtain a model consisting of two Bi $6p$ and two S $3p$ orbitals, which give nearly electron-hole symmetric bands. Further focusing on the bands that intersect the Fermi level, we obtain a model with two p orbitals. The two bands (per BiS₂ layer) have quasi-one-dimensional character with a double minimum dispersion, which gives good nesting of the Fermi surface. At around $x \sim 0.5$ the topology of the Fermi surface changes, so that the density of states at the Fermi level becomes large. Possible pairing states are discussed.

For the past several decades, superconductors with layered lattice structures such as the cuprates[1], organic conductors[2], MgB₂[3], Sr₂RuO₄[4], Na_xCoO₂[5], (Hf,Zr)NCI[6], and iron pnictides[7] have attracted much attention. These layered superconductors have been of interest in many aspects like high T_c and/or unconventional pairing mechanisms. Quite recently, Mizuguchi *et al.* have discovered superconducting materials that possess BiS₂ layers, where the Bi and S atoms are aligned alternatively on a square lattice. The materials found so far are Bi₄O₄S₃[8] and LaO_{1-x}F_xBiS₂[9] which have T_c of 8.6K and 10.6K, respectively. Fig.1 shows the lattice structure of LaOBiS₂, where partial replacement of O by F ($x = 0.5$) provides electron doping and gives rise to superconductivity. These findings strongly suggest that materials with BiS₂ layers provide yet another family for layered superconductors exhibiting double-digit T_c , and it is of special importance to understand the underlying electronic structure of these materials.

Recent theoretical studies on superconductivity have shown that effective models constructed from first principles band calculation can provide solid basis for the study on the mechanism of superconductivity, especially for materials with complicated band structures such as the iron pnictides[10]. In the present paper, we perform first principles band calculation of LaOBiS₂, from which we construct maximally localized Wannier orbitals to obtain the effective tightbinding models, i.e., the electron kinetic energy part of the effective Hamiltonian. The models consist of two or four bands that have quasi-one-dimensional character, which are hybridized to give a two dimensional Fermi surface. At around $x \sim 0.5$ the topology of the Fermi surface changes, so that the density of states at the Fermi level becomes large. We show that the quasi-one-dimensional nature results in a nesting of the Fermi surface, which gives rise to enhanced irreducible susceptibility along the diagonals that intersects the wave vectors $(0, 0)$ and (π, π) . We discuss possible superconducting states.

First principles band calculation of the mother compound LaOBiS₂ is performed using the Wien2K package[11] and adopting the lattice structure given in

ref.[12]. Space group is P4/nmm and $a = 4.05\text{\AA}$, $c = 13.74\text{\AA}$. La, S and Bi take the 2b positions with $z_{La} =$

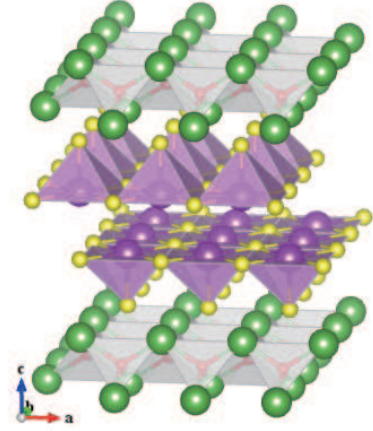


FIG. 1. The lattice structure of LaOBiS₂.

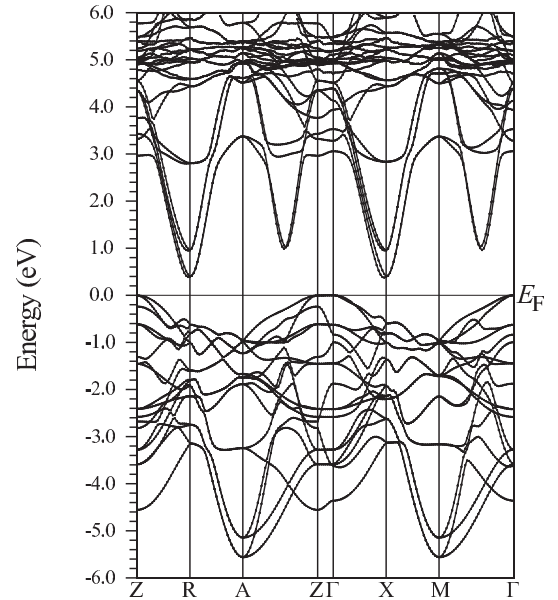


FIG. 2. The first principles band structure is shown.

0.0936, $z_{S_1} = 0.813$, $z_{S_2} = 0.379$ and $z_{Bi} = 0.6263$, and O takes the 2a position. Here we present results without the spin-orbit coupling, although this coupling does have some effect on the band structure. The calculation result is shown in Fig.2. The conduction bands around the Fermi level consists mainly of in-plane Bi 6*p* orbital character, mixed with in-plane S 3*p*.

From this band calculation, we obtain maximally localized Wannier orbitals[13, 14], which enables us to construct tightbinding models that correctly reproduces the original first principles band structure around the Fermi level. First, we construct a 24 orbital model, which consists of six Bi 6*p*, twelve S 3*p* and six O 2*p* orbitals. The band structure of the obtained tight binding model is shown in Fig.3(a). Here, the thickness of the lines represent the weight of the in-plane *p* orbitals within the BiS₂ layers. Since the BiS₂ layers are without doubt the origin of the superconductivity, we can further obtain a model that omits the O 2*p* orbitals, the 3*p* orbitals of the out-of-plane S, and also the *p_z* orbital of the in-plane S (whose bands lie away from the Fermi level), and we are left with an eight orbital model (band not shown). There are eight orbitals because there are two BiS₂ layers per unit cell, and each Bi and in-plane S has two *p* orbitals.

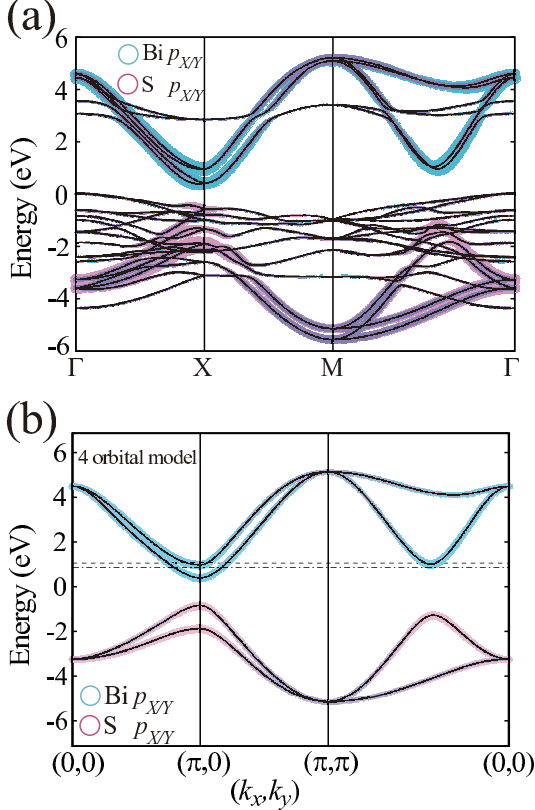


FIG. 3. (a) The 24 orbital model and (b) the four orbital model. In (b), the dashed (dotted-dashed) lines denote the Fermi energy for the doping ratio $\delta = 0.5$ ($\delta = 0.25$).

By further neglecting the small interlayer coupling be-

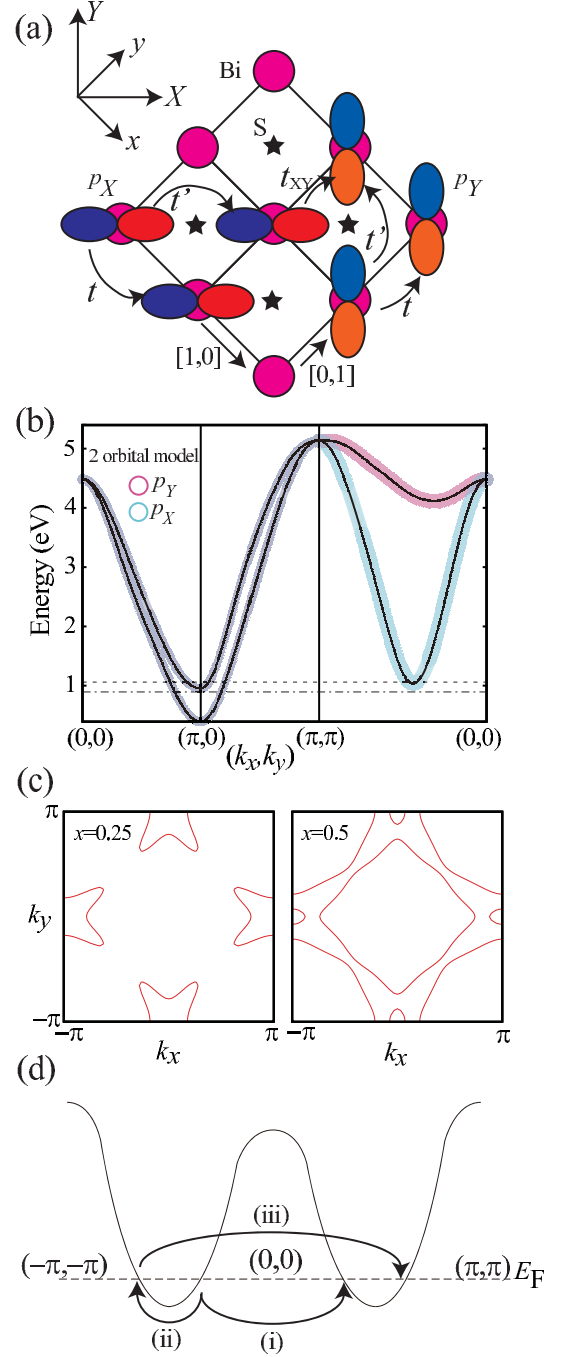


FIG. 4. (a) The tightbinding model on the Bi square lattice is shown along with the hoppings of p_X and p_Y orbitals. The stars denote the position of the S atom, whose *p* orbitals are explicitly considered in the four orbital model, but are integrated out in the two orbital model. (b) The band structure of the two orbital model. The dashed (dotted-dashed) lines denote the Fermi energy for the doping ratio $\delta = 0.5$ ($\delta = 0.25$). (c) The Fermi surface of the two orbital model for the doping rate of $\delta = 0.25$ and $\delta = 0.5$. (d) A schematic figure of the p_X band along $(-\pi, -\pi) \rightarrow (0, 0) \rightarrow (\pi, \pi)$. Three types of nesting vectors are shown by the arrows.

tween the neighboring BiS₂ layers, we end up with a two-dimensional “*p-p*” four orbital model consisting of two Bi 6*p* and two S 3*p* orbitals. The band structure of this model is shown in Fig.3(b). We write the model Hamiltonian in the form

$$H_0 = \sum_{ij} \sum_{\mu\nu} \sum_{\sigma} \left[t(x_i - x_j, y_i - y_j; \mu, \nu) c_{i\mu\sigma}^\dagger c_{j\nu\sigma} + t(x_j - x_i, y_j - y_i; \nu, \mu) c_{j\nu\sigma}^\dagger c_{i\mu\sigma} \right] + \sum_{i\mu\sigma} \varepsilon_{i\mu} n_{i\mu\sigma}, \quad (1)$$

where $c_{i\mu\sigma}^\dagger$ creates an electron with spin σ on the μ -th orbital in the i -th unit cell, and $n_{i\mu\sigma} = c_{i\mu\sigma}^\dagger c_{i\mu\sigma}$. Then, the parameters of this four orbital model is given in table I. The two *p* orbitals are denoted as p_X and p_Y , where the X - Y axis are rotated by 45 degrees from the x - y axes (an figure of the four orbital model is not presented, but see Fig.4(a) for the X and Y axes.) It is interesting to note that the upper and the lower bands are roughly symmetric with respect to the gap.

Even more simple model is the one which focuses only on the bands that intersect the Fermi level. By extracting these bands using the maximally localized Wannier orbitals centered at the Bi sites and neglecting the inter-layer hoppings, the Hamiltonian reduces to a two dimensional two orbital model (Fig.4(a)), whose band structure is shown in Fig.4(b) and the hopping parameters given in table II. Assuming a rigid band, the Fermi surface for this model is obtained in Fig.4(c) for two doping ratios $\delta = 0.25$ and $\delta = 0.5$. Here δ is defined as the number of doped electrons per Bi site, and satisfies $\delta = x$ in an ideal situation. At around $\delta \sim 0.5$ the topology of the

TABLE I. Hopping parameters $t(\Delta x, \Delta y; \mu, \nu)$ or the on-site energies ε_μ for the four orbital model. The orbitals $\mu = 1, 2, 3, 4$ correspond to Bi p_Y , p_X , S p_Y , p_X orbitals, respectively. We follow the notations in ref.[10], i.e., I , and σ_d corresponds to $t(-\Delta x, -\Delta y; \mu, \nu)$, $t(\Delta y, \Delta x; \mu, \nu)$, respectively, where ‘ $\pm$ ’ means that the corresponding hopping is equal to $\pm t(\Delta x, \Delta y; \mu, \nu)$, respectively.

(μ, ν)	$[\Delta x, \Delta y]$					I	σ_d
	[0,0]	[1,0]	[-1,0]	[1,-1]	[1,1]		
(1,1)	0.890	0.223	0.223	0.103	0.082	+	+
(1,2)		0.100	0.100			+	-
(1,3)	0.486		-2.034			+	+
(1,4)						+	+
(2,2)	0.890	0.223	0.223	0.082	0.103	+	+
(2,3)						+	+
(2,4)	2.034		-0.486			+	+
(3,3)	-1.113	-0.110	-0.110	0.100	0.023	+	+
(3,4)		0.154	0.154			+	-
(4,4)	-1.113	-0.110	-0.110	0.023	0.100	+	+

TABLE II. Hopping parameters and on-site energies for the two orbital model. $\mu = 1, 2$ correspond to p_Y , p_X , respectively. Here $t' = 0.880$, $t = -0.167$, and $t_{XY} = 0.107$

(μ, ν)	$[\Delta x, \Delta y]$							I	σ_d
	[0,0]	[1,0]	[1,-1]	[1,1]	[2,0]	[2,1]	[2,-1]		
(1,1)	2.811	-0.167	0.880	0.094		0.014	0.069	+	+
(1,2)		0.107			-0.028	0.020	0.020	+	-
(2,1)		0.107			-0.028	0.020	0.020	+	-
(2,2)	2.811	-0.167	0.094	0.880		0.069	0.014	+	+

Fermi surface changes, so that the density of states at the Fermi level becomes large around this band filling. The p_X and p_Y bands have essentially one-dimensional character, where the main hopping integrals (t') exist between next nearest neighbor sites, as shown in Fig.4(a) and table II. Thus the one-dimensional bands essentially have the forms

$$\varepsilon_X(k) = 2t' \cos(k_x + k_y), \quad \varepsilon_Y(k) = 2t' \cos(k_x - k_y) \quad (2)$$

which has a double well band dispersion along $(k_x, k_y) = (-\pi, -\pi) \rightarrow (0, 0) \rightarrow (+\pi, +\pi)$ or $(-\pi, +\pi) \rightarrow (0, 0) \rightarrow (+\pi, -\pi)$, as shown in Fig.4(d). The intra-orbital (t) as well as the inter-orbital (t_{XY}) nearest neighbor hoppings give the two dimensionality of the system.

The one-dimensional nature of the bands provides good nesting of the Fermi surface. To see this effect, we calculate for the two orbital model the 4×4 irreducible susceptibility matrix as k summation of the product of the 2×2 Green’s function matrix. In Fig.5, we show the largest eigenvalue of the irreducible susceptibility matrix for the doping ratio of $\delta = 0.25$ and $\delta = 0.5$. The diagonal structures that go through $(0, 0)$ or (π, π) are due to the nesting shown by the arrows in Fig.4(d). Note that if the nearest neighbor hoppings do not exist and the bands have the form in eq.(2), the nestings (i)~(iii) are equivalent, while this equivalence is lost in the presence of t (and additional hoppings).

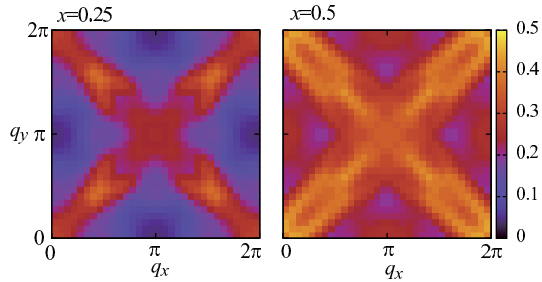


FIG. 5. The largest eigenvalue of the irreducible susceptibility matrix for $\delta = 0.25$ and 0.5 .

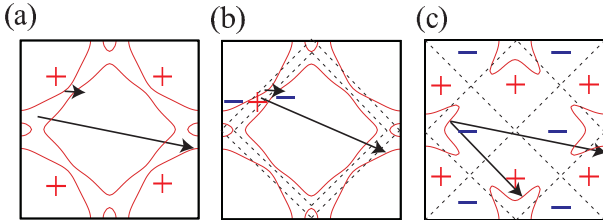


FIG. 6. (a) sign conserving *s*-wave (b) sign reversing *s*-wave, and (c) *d*-wave superconducting gaps.

Finally, let us discuss the possible pairing states and the superconducting gap structure. Since the many-body term of the effective Hamiltonian is not determined here, there are several possibilities at present. The most relevant bands have mainly $6p$ character, which gives wide spread of the Wannier orbitals, so that the electron-electron interactions may not be very strong and short-ranged as in the $3d$ -orbital based materials such as the cuprates and iron-based superconductors. In that case, the electron-phonon interaction can be playing the main role in the Cooper pairing, and the good nesting of the Fermi surface may cooperate to give enhanced attractive pairing interaction around the nesting vectors. This, combined with the large density of states for $x \sim 0.5$ due to the change in the topology of the Fermi surface, can give rise to a s -wave pairing with constant gap sign as shown in Fig.6(a). A more exotic possibility for the same type of gap is related to the fact that the system is close to a band insulator, where electron-hole excitations might be playing an important role in the pairing[25]. In fact, if we consider electron-electron interactions in the four orbital model, the system can be viewed as two interacting charge-transfer-type insulating bands. This is similar to the situation studied in ref.[26], where the occurrence of superconductivity was proposed for systems with a metallic band interacting with a charge-transfer-type insulating band. In this context, it should be noted that the analysis for the Bi $6p$ -S $3p$ four orbital model can give different results from those for the two orbital model regarding the superconducting state, because the band filling is different, i.e., the four orbital model is a nearly half-filled, electron-hole symmetric system, while the two orbital model has small band filling.

On the other hand, if we assume a short ranged repulsive interaction, the present two orbital model provides a fundamental problem of the pairing state in repulsively interacting quasi-one-dimensional systems, apart from its relevance to the BiS₂ layers. Namely, the occurrence of superconductivity in repulsively interacting one-dimensional systems with a double well type band structure was studied in the late 1990's, where the interaction (ii) in Fig.4(d) dominates for certain parameter regime to give a gap that reverses its sign between the inner and the outer Fermi points[17–20]. The existence of t in Fig.4(a) is essential in this case, because this makes the interactions (i)/(iii) and (ii) inequivalent. In fact, by adding on-site intra- (U) and inter-orbital interactions ($U' = 2U/3$ and the Hund's coupling and the pair hoppings $J = J' = U/6$), and applying multiorbital random phase approximation[15, 16] to obtain the spin-fluctuation-mediated pairing interaction, we find the sign reversing s -wave gap shown in Fig.6(b) for $\delta = 0.5$ and $U = 2.43\text{eV}$ and the d -wave superconducting gap shown in Fig.6(c) $\delta = 0.25$ and $U = 1.8\text{eV}$. These gaps are formed by cooperation/competition between the repulsive (sign reversing) spin-singlet pairing interactions

driven by the nestings given in Fig.4(d). The gap (b) indeed exhibits sign reverse between the inner and the outer Fermi surfaces. On the other hand, gap (c) is obtained by reversing the gap sign for both interactions (i) and (ii). To make the gap have even parity requires additional nodes at $k_x = \pm k_y$ which do not intersect the Fermi surface for small doping ratio.

Finally, yet another possibility related with the quasi-one-dimensionality is the spin-triplet pairing. In fact, the present band structure also has similarity with the quasi-one-dimensional bands (the hybridized $d_{xz/yz}$ bands) in Sr₂RuO₄, where some theoretical studies have suggested the possibility of spin-triplet pairing originating from these bands[21–24]. Nuclear magnetic resonance experiments will provide a test for this possibility.

To summarize, we have obtained effective tightbinding models for the newly discovered superconducting BiS₂ layers by performing first principles band calculation for LaOBiS₂ and exploiting the maximally localized Wannier orbitals. The model consists of p_X and p_Y orbitals, and the dominant next nearest neighbor hoppings lead to quasi-one-dimensional bands, which give relatively strong nesting of the Fermi surface. Considering the quasi-one-dimensional as well as the doped-band-insulator nature of the band structure, there are several interesting possibilities of the superconducting state depending on the dominating many-body interactions.

ACKNOWLEDGMENTS

We are grateful to Y. Mizuguchi for showing us the experimental results for LaO_{1-x}F_xBiS₂ prior to publication. We also acknowledge all the collaborators in ref.[8]. This study has been supported by Grants-in-Aid for Scientific Research from MEXT of Japan and from the Japan Society for the Promotion of Science.

-
- [1] J.G. Bednorz and K.A. Muller, Z. Phys. B Cond. Matt. **64** 189 (1986).
 - [2] For a recent review, see A. Ardavan *et al.*, J. Phys. Soc. Jpn. **81**, 011004 2012.
 - [3] J. Nagamatsu *et al.*, Nature **410**, 63 (2001).
 - [4] Y. Maeno *et al.*, Nature **372**, 532 (1994).
 - [5] K. Takada *et al.*, Nature **422**, 53 (2003).
 - [6] S. Yamanaka, K. Hotehama, and H. Kawaji, Nature **392**, 580 (1998).
 - [7] Y. Kamihara *et al.*, J. Am. Chem. Soc. **130**, 3296 (2008).
 - [8] Y. Mizuguchi *et al.*, arXiv: 1207.3145
 - [9] Y. Mizuguchi *et al.*, arXiv: 1207.3558.
 - [10] K. Kuroki *et al.*, Phys. Rev. Lett. **101**, 087004 (2008).
 - [11] P. Blaha, K. Schwarz, G.K.H. Madsen, D. Kvasnicka, and J. Luitz, *Wien2k: An Augmented Plane Wave + Local Orbitals Program for Calculating Crystal Properties* (Vienna University of Technology, Wien, 2001). Here we take

- $RK_{\max} = 7$, 512 k -points, and adopt the exchange correlation functional introduced by J. P. Perdew, K. Burke, and M. Ernzerhof [Phys. Rev. Lett. **77**, 3865 (1996)].
- [12] V.S. Tanryverdiev and O.M. Aliev, Inorg. Mater. **31**, 1361 (1995).
 - [13] N. Marzari and D. Vanderbilt, Phys. Rev. B **56**, 12847 (1997); I. Souza, N. Marzari, and D. Vanderbilt, Phys. Rev. B **65**, 035109 (2001). The Wannier functions are generated by the code developed by A. A. Mostofi, J. R. Yates, N. Marzari, I. Souza, and D. Vanderbilt, (<http://www.wannier.org/>).
 - [14] J. Kunes, R. Arita, P. Wissgott, A. Toschi, H. Ikeda, and K. Held, Comp. Phys. Commun. **181** 1888 (2010).
 - [15] T. Takimoto, T. Hotta, and K. Ueda, Phys. Rev. B **69**, 104504 (2004).
 - [16] K. Yada and H. Kontani, J. Phys. Soc. Jpn. **74**, 2161 (2005).
 - [17] M. Fabrizio, Phys. Rev. B **54**, 10054 (1996).
 - [18] K. Kuroki, R. Arita, and H. Aoki, J. Phys. Soc. Jpn. **66**, 3371 (1997).
 - [19] K. Sano *et al.*, J. Phys. Soc. Jpn. **74**, 2885 (2005).
 - [20] T. Nakano, K. Kuroki, and S. Onari, Phys. Rev. B **76**, 014515 (2007).
 - [21] T. Kuwabara and M. Ogata, Phys. Rev. Lett. **85**, 4586 (2000).
 - [22] M. Sato and M. Kohmoto, J. Phys. Soc. Jpn. **69**, 3505 (2000).
 - [23] K. Kuroki *et al.*, Phys. Rev. B **63**, 060506(R) 2001.
 - [24] T. Takimoto, Phys. Rev. B **62**, 14641(R) (2000).
 - [25] W.A. Little, Phys. Rev. **134**, A1416 (1964).
 - [26] K. Kuroki and H. Aoki, Phys. Rev. B **48**, 7598 (1993).